

HIPERCO® 50

Type analysis

Single figures are nominal except where noted.

Iron	Balance	Cobalt	48.5 %	Vanadium	1.9 %
Niobium	0.05 %	Carbon	0.01 %		

Forms manufactured

Strip	Plate
--------------	--------------

Additional details available on page 5, Other Information.

Description

Hiperco 50 is an iron-cobalt vanadium soft magnetic alloy that exhibits the highest magnetic saturation (24 kilogauss) of commercially available soft magnetic alloys while maintaining low core loss as compared to electrical steel. This alloy is produced in strip, plate, and slab form and contains a small niobium addition to control grain growth during heat treatment, which allows for varying levels of mechanical strength and magnetic properties.

Hiperco 50 is used in motors and generators for achieving maximum torque density and minimum losses. It helps improve motor power density and efficiency, and can reduce the size of the motor. This alloy also offers the highest forces for actuators in consumer electronic applications, such as speaker, haptic, and sensor devices.

Key Properties:

- High magnetic saturation
- Low core loss compared to electrical steel
- Mechanical strength

Markets:

- Aerospace
- Automotive
- Consumer
- Industrial

Applications:

- Motors
- Generators
- Actuators
- Magnetic bearings

> HIPERCO 50

Standard magnetic anneal physical properties

PROPERTY	At or From	English Units	Metric Units
SPECIFIC GRAVITY	68°F (20°C)	8.12	8.12
DENSITY	—	0.2930 lb/in ³	8.11 g/cm ³
MEAN COEFFICIENT OF THERMAL EXPANSION	77 to 392°F (25 to 200°C)	5.3 x 10 ⁻⁶ /°F	9.59 x 10 ⁻⁶ /°C
	77 to 752°F (25 to 400°C)	5.6 x 10 ⁻⁶ length/length/°F	10.1 x 10 ⁻⁶ length/length/°C
	77 to 1112°F (25 to 600°C)	5.8 x 10 ⁻⁶ length/length/°F	10.5 x 10 ⁻⁶ length/length/°C
	77 to 1472°F (25 to 800°C)	6.3 x 10 ⁻⁶ length/length/°F	11.3 x 10 ⁻⁶ length/length/°C
THERMAL CONDUCTIVITY	—	206.8 Btu in/hr/ft ² /°F	29.83 W/m/°C
ELASTIC MODULUS	—	30 x 10 ³ ksi	206.8 GPa
ELECTRICAL RESISTIVITY	70°F (21°C)	241.0 ohm-cir-mil/ft	40.1 x 10 ⁻⁸ ohm-m
CURIE TEMPERATURE¹	—	1720°F	938°C

¹ Curie temperature is phase transition from magnetic to non-magnetic phase

Magnetic properties

AC CORE LOSS

HEAT TREATMENT	CORE LOSS BY HEAT TREATMENT						B (TESLA)
	0.014 IN (0.355 MM)			0.006 IN (0.1524 MM)			
	SPECIFIC CORE LOSS (W/kg)			SPECIFIC CORE LOSS (W/kg)			
	60 Hz	400 Hz	1000 Hz	60 Hz	400 Hz	1000 Hz	
Standard magnetic anneal	1.11	13.3	54.1	1.17	10.2	33.9	1.0
	2.03	29.8	142	2.08	19.2	65.8	1.5
	3.29	56.7	301	3.32	30.9	109	2.0
Standard mechanical anneal	2.48	23.0	80.2	2.17	16.7	46.2	1.0
	4.47	47.5	191	3.96	31.1	93.8	1.5
	7.16	84.5	388	6.54	51.4	157	2.0


> HIPERCO 50

DC PROPERTIES
0.014 IN (0.355 MM) STRIP

HEAT TREATMENT	COERCIVITY (A/m) FROM 8 kA/m	DC RELATIVE PERMEABILITY μ_{MAX}	B (TESLA) A/m					
			400	800	1600	4000	8000	16000
Standard magnetic anneal	40	19200	2.12	2.19	2.23	2.27	2.28	2.30
Standard mechanical anneal	125	7900	2.01	2.12	2.19	2.25	2.28	2.29

0.006 IN (0.1524 MM) STRIP


HEAT TREATMENT	COERCIVITY (A/m) FROM 8 kA/m	DC RELATIVE PERMEABILITY μ_{MAX}	B (TESLA) A/m					
			400	800	1600	4000	8000	16000
Standard magnetic anneal	50	15000	2.03	2.14	2.21	2.27	2.28	2.30
Standard mechanical anneal	125	7400	1.99	2.11	2.18	2.25	2.28	2.29

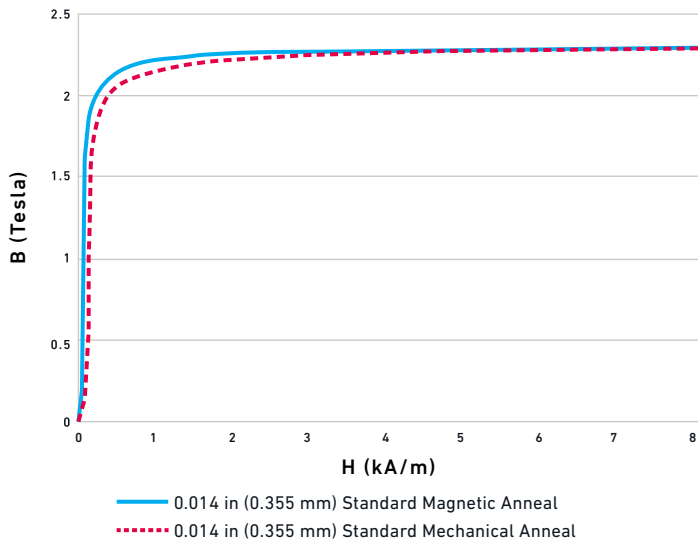DC B v H


> HIPERCO 50

DC RELATIVE PERMEABILITY

- 0.014 in (0.355mm) standard magnetic anneal
- - - 0.014 in (0.355mm) standard mechanical anneal

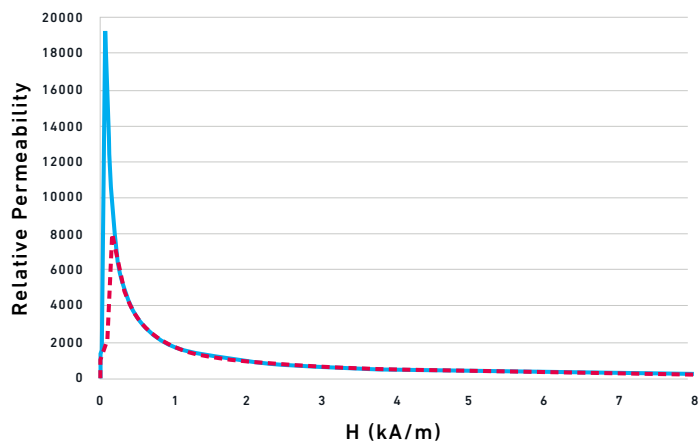

> HIPERCO 50

Typical mechanical properties

0.014 IN (0.355 MM) STRIP						
HEAT TREATMENT	0.2% YIELD STRENGTH		ULTIMATE TENSILE STRENGTH		ELONGATION IN 2 IN (50.8 MM)	HARDNESS
	ksi	MPa	ksi	MPa	%	ROCKWELL C
Cold rolled unannealed	175	1270	190	1310	2	36
Standard magnetic anneal	48	331	115	792	5-15	—
Standard mechanical anneal	60	414	135	930	5-15	—

0.006 IN (0.1524 MM) STRIP						
HEAT TREATMENT	0.2% YIELD STRENGTH		ULTIMATE TENSILE STRENGTH		ELONGATION IN 2 IN (50.8 MM)	HARDNESS
	ksi	MPa	ksi	MPa	%	ROCKWELL C
Cold rolled unannealed	190	1310	205	1413	1	40
Standard magnetic anneal	45	310	115	792	5-15	—
Standard mechanical anneal	56	386	135	930	5-15	—

Heat treatment

Annealing

It is important to avoid any contamination of the finished parts during heat treatment. All parts must be cleaned thoroughly to remove any surface contaminants prior to annealing.

A dry hydrogen atmosphere or high vacuum is recommended to minimize oxide contamination during annealing. When hydrogen is employed and the inside retort temperature is above 900°F (482°C), the entry dew point should be dryer than -60°F (-51°C) and the exit dew point should be dryer than about -40°F (-40°C).

Anneal parts at 1300/1600°F (704/871°C) for 2 to 4 hours in dry hydrogen or vacuum and cool at 250/400°F (139/222°C) per hour until 600°F (316°C) is reached, after which any cooling rate can be employed. The exact heat treat temperature used will depend on the particular application and the desired compromise between magnetic and mechanical properties. Increasing temperature within the range of 1300 to 1600°F (704 to 871°C) will result in improved magnetic properties and decreased yield and tensile strengths. However, the temperature should never exceed 1600°F (871°C), as soft magnetic characteristics will start to decline due to formation of an austenitic phase.

> HIPERCO 50

Coatings

Inlac	Inlac coating is applied in a continuous process on coils of strip to create a mix of magnesium-based compounds on both sides of the strip surface. This surface layer acts as an inert barrier between laminations during heat treating and prevents adhesion. Additionally, during AC excitation, it provides improved electrical insulation between laminations reducing eddy current effects on core loss.
Oxide	Annealed laminations can be heat treated in an oxygen bearing atmosphere in the range of 600 to 900°F (316 to 480°C) to grow a thin oxide layer on the surface. This coating provides an enhanced level of electrical insulation between laminations, greatly reducing eddy current effects during AC excitation. Oxide heat treatment soak times are generally less than 5 hours and can be adjusted to refine coating thickness.

Other information

Applicable specifications	ASTM A801 Alloy Type 1, MIL A 47182
----------------------------------	-------------------------------------

Appendix

PHYSICAL PROPERTIES	ASTM STANDARD #
Density	B311-17
Coefficient of thermal expansion	E228
Thermal conductivity	ASTM E1225 - 13
Modulus of elasticity	ASTM A370 Section 14, E8-E8M
Electrical resistivity	B193
Curie temperature	A 894/A 894M-00
AC magnetic properties	A927/A927M
DC magnetic properties	A596/A596M
Mechanical properties	E8, A677 Section 9

**For additional information, please
contact your nearest sales office:**

electrification@cartech.com | 610 208 2000

The information and data presented herein are typical or average values and are not a guarantee of maximum or minimum values. Applications specifically suggested for material described herein are made solely for the purpose of illustration to enable the reader to make their own evaluation and are not intended as warranties, either express or implied, of fitness for these or other purposes. There is no representation that the recipient of this literature will receive updated editions as they become available.

Unless otherwise specified, registered trademarks are property of CRS Holdings Inc., a subsidiary of Carpenter Technology Corporation.
